

111-textured BaTiO₃ ceramics elaborated by Templated Grain Growth using NaNbO₃ templates

A Ngueteu-Kamlo, Pierre-Marie Geffroy, M Pham-Thi, Pascal Marchet

► **To cite this version:**

A Ngueteu-Kamlo, Pierre-Marie Geffroy, M Pham-Thi, Pascal Marchet. 111-textured BaTiO₃ ceramics elaborated by Templated Grain Growth using NaNbO₃ templates. *Materials Letters*, Elsevier, 2013, 113, pp.149-151. 10.1016/j.matlet.2013.09.071 . hal-01097352

HAL Id: hal-01097352

<https://hal-unilim.archives-ouvertes.fr/hal-01097352>

Submitted on 5 Jan 2015

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

{111}-textured BaTiO₃ ceramics elaborated by Templated Grain Growth using NaNbO₃ templates

A. Ngueteu Kamlo^a, P-M. Geffroy^a, M. Pham-Thi^b, P. Marchet^{a,*}

^a CNRS - Université de Limoges, Science des Procédés Céramiques et de Traitements de Surface, UMR 7315, Centre Européen de la Céramique, 12 Rue Atlantis, 87068 Limoges Cedex, France

^b THALES Research & Technology France, Campus Polytechnique, 1, avenue Augustin Fresnel - 91767 Palaiseau Cedex - France

* Corresponding author:

Phone: +33 5 87502373

E-mail address: pascal.marchet@unilim.fr

Abstract

Highly textured {111} BaTiO₃ ceramics were obtained by templated grain growth using NaNbO₃ templates, with Lotgering factor F_{111} , around 95 %, one of the best values reported in the literature. Solid solution formation with NaNbO₃ templates changes the tetragonal structure into cubic, with paraelectric behaviour. The relative permittivity is lower than "pure" tetragonal BaTiO₃, but dielectric losses are improved with better thermal stability.

Keywords

Electroceramics, Texture, Templated Grain Growth, Tape casting

1. Introduction

Lead-free BaTiO₃ (BT) based perovskite materials present potential interest in numerous domains because of their dielectric, ferroelectric and piezoelectric properties. To improve the properties of such anisotropic materials, particular attention has been paid to textured microstructures in ceramic materials (i.e. grain orientation) [1, 2, 3]. Thus different texturation methods were developed: directional solidification technology [4], hot forging [2], Templated Grain Growth (TGG) [5, 6], Reactive Templated Grain Growth (RTGG) [6]... In order to orientate templates, different techniques were developed: slip casting, tape casting, extrusion centrifugal casting [7, 8]. These methods were reported for texturation of lead free materials, particularly for


$\text{Na}_{0.5}\text{Bi}_{0.5}\text{TiO}_3\text{-BaTiO}_3$ system [6, 9], but rarely for pure BaTiO_3 . RTGG was successfully used for elaboration of {111} oriented BaTiO_3 ceramic [10], using reactive sintering between plate-like $\text{Ba}_6\text{Ti}_{17}\text{O}_{40}$ and BaCO_3 and for {110} oriented BaTiO_3 using needlelike TiO_2 particles [11]. However, dense ceramics are difficult to obtain due to decarbonation during sintering (only 81 %) [12]. {111} textured BaTiO_3 ceramics were elaborated with plate-like BaTiO_3 templates and powder using TGG method, with relative density around 95 % of the theoretical one [13].

Nowadays, NaNbO_3 templates (NN) were successfully used for the texturation of alkaline niobate ceramics [14-16], but not for BaTiO_3 . Thus, the aim of this work is (i) to obtain highly densified and highly textured BaTiO_3 ceramics by TGG process using NaNbO_3 templates and (ii) to investigate the structure and electrical properties of such anisotropic ceramics.

2. Experimental procedure

2.1. Synthesis of NaNbO_3 platelets and BaTiO_3 powders

NaNbO_3 platelets were synthesized using a process derived from the one previously reported [17]. $\text{Bi}_{2.5}\text{Na}_{3.5}\text{Nb}_5\text{O}_{18}$ platelets (BNN5) were synthesized by Molten Salt Synthesis. Analytical grades NaCO_3 , Bi_2O_3 and Nb_2O_5 were weighed in stoichiometric proportions, mixed with NaCl in anhydrous ethanol (oxide to salt weight ratio 1: 1.5) and heated at 1130 °C for 5 h in sealed alumina crucible. The remaining flux salt was then removed by washing several times with de-ionized water, until total removing of chloride ions. BNN5 platelets were then converted into NaNbO_3 templates by Topochemical Conversion (TC). This topotactic transformation preserves the initial morphology of BNN5 grains [17]. It corresponds to chemical reaction:



BNN5 microcrystals were mixed with 10 % excess Na_2CO_3 , according to stoichiometry of the reaction. NaCl was added as flux (oxide to salt weight ratio 1:1.5). The mixture was heated at 1000 °C for 6 h in sealed alumina crucible and then washed

several times using hot de-ionised water. The NN templates were separated using HCl (8 M), in order to dissolve Bi_2O_3 produced during TC reaction. Microstructures of BNN5 platelets and NN templates (fig. 1.a and b) consist of anisotropic platelets with 5-15 μm length and around 1 μm thickness, close to those previously reported [17].

Equiaxial BaTiO_3 powder was obtained with low particle size 80 - 100 nm by solid state route at 900 °C. Splitting of the diffraction peaks (Fig. 2) confirms tetragonal structure: lattice parameters "a" = 0.4000 ± 0.0001 nm, "c" = 0.4022 ± 0.0002 nm, similar to reference values of tetragonal BaTiO_3 (a = 0.3994 nm, c = 0.4038 nm, JCPDS # 05-626).

2.2. Texturation of the ceramics by TGG

The tape casting slurry was prepared using non-aqueous formulation (volume ratio powder / templates 92:8) optimized in previous work [18] against organic way for reported results [10-13]. The large viscosity of the suspension ($1 \text{ Pa}\cdot\text{s}^{-1}$) and shearing stresses during casting led to the orientation of anisotropic NN templates in casting direction. The process includes the following steps: (i) first mixing of the suspension was performed 1h by using low rotation speed to avoid breaking templates, (ii) after adding binder + plasticizer, second mixing was performed by planetary milling at low rotation speed for 17 h, (iii) after degassing (24h), slurry was tape-casted onto a siliconed Mylar carrier film (doctor blade opening 600 μm , speed $2 \text{ m}\cdot\text{mn}^{-1}$), (iv) tapes were dried at room temperature in a solvent saturated enclosure and (v) samples were cut and stacked by thermo-compression (50 °C - 60 MPa). The obtained pellets were then sintered using a two steps process: (i) carefully burning out of the organic additives (dispersant, binder and plasticizer) between 100 and 500°C (20°C/h) and (ii) sintering at 1150 °C for 10 h (200°C/h).

3. Results and discussion

As a matter of comparison with TGG process, a reference sample with the same powder: templates ratio was elaborated by conventional ceramic route without tape casting, using traditional uniaxial pressing. All samples were sintered at the same temperature.

Figure 2 presents XRD of BaTiO₃ powder, reference and textured samples, respectively. The splitting of (001) peaks observed at 20° and 45° for powder are characteristic of tetragonal symmetry, while single peaks associated to cubic phase are observed for both reference and textured samples. The cubic symmetry obtained for both samples indicates that during sintering process, BaTiO₃ tetragonal phase was transformed into cubic one. This structure-modification can be attributed to the formation of a solid solution with NaNbO₃ templates, since same symmetry is obtained by conventional and TGG process. Indeed, structural refinement (Rietveld method, reference ceramic) led to Ti⁴⁺ / Nb⁵⁺ content around (87 ± 1) : (13 ± 1) mol% in B-site of the perovskite lattice. Similar behavior has been reported for Niobium-doped BaTiO₃ ceramics: above 0.8% Nb₂O₅ the structure changes from tetragonal to pseudo-cubic [19]. The calculated lattice parameter are "a" = 0.4001 ± 0.0002 nm for TGG ceramic and "a" = 0.4012 ± 0.0001 nm for reference ceramic respectively, close to those of cubic BaTiO₃ (a= 0.4031 nm, JCPDS # 031-0174).

X-ray diffraction pattern of TGG ceramic (surface of the sample parallel to casting direction), clearly shows major cubic perovskite phase and minor unidentified phase (fig. 2). The perovskite phase presents a strong (111) peak, characteristic of {111} preferential orientation, thus demonstrating efficiency of the texturation process. This result confirms that the tetragonal to cubic structure-modification can be attributed to the formation of a solid solution with NaNbO₃ templates while texturation is induced by orientation of templates by tape casting.

{111} texturation degree was evaluated around 95% using the Lotgering factor [20] by taking cubic BaTiO₃ as reference (JCPDS # 031-0174). This value is higher than 80% previously obtained by RTGG [10, 12] and 36% by TGG [13]. In the SEM micrograph (fig.2c), the fractured sintered textured sample appears as well densified and exhibits a particular direction of grain growth, according with the high texturation degree.

Dielectric properties were measured from 100 Hz to 1 MHz using an impedance analyser. Variation of relative permittivity and dielectric loss versus temperature are presented in fig. 3. The measurements revealed linear decrease for BaTiO₃- 8% NaNbO₃ textured ceramic, compared with the well-known accident near 400 K for undoped BaTiO₃ ceramic associated to tetragonal-cubic phase transition at Curie temperature. Paraelectric behaviour observed for BaTiO₃- 8% NaNbO₃ textured ceramic is characteristic of non-ferroelectric material, in good agreement with cubic structure observed by XRD.

Curie-Weiss plot of ϵ^{-1} versus T clearly confirms the paraelectric behaviour for the BaTiO₃- 8% NaNbO₃ textured sample, with a change of slope around 408 K (fig.3 b). Calculations were performed using Curie-Weiss law, $\epsilon^{-1} = (T-T_0) / C$, ϵ = relative permittivity, T = temperature (K), T₀ and C = Curie-Weiss temperature and constant. The results (table 1, T₀, C) are different from those obtained for "pure" BaTiO₃. This suggests that the anomaly can't be attributed to BaTiO₃ phase transition but likely comes from minor unidentified secondary phase. Finally, the dielectric losses are improved, (1-1.5%), and present good thermal stability, contrary to "pure" BaTiO₃.

Conclusion

Highly textured {111} BaTiO₃ ceramics were successfully elaborated by TGG method using NaNbO₃ templates. Optimization of the processing parameters allowed obtaining reproductively a high degree of {111} orientation with Lotgering factor, F₁₁₁,

around 95 % (details about optimization will be published elsewhere). X-ray diffraction revealed a cubic structure, confirmed by the paraelectric behaviour of the textured ceramic. Finally, compared to "pure" BaTiO₃, the relative permittivity is slightly decreased but the dielectric losses are improved, with better thermal stability. Thus the most important results of this study are: (i) the very high degree of texturation, around 95%, one of the best values reported today in literature and (ii) the improvement of the dielectric losses with better thermal stability.

Acknowledgement: The authors kindly acknowledge financial support from the French Research National Agency (ANR), project HYPERCAMPUS

References

- [1] Youngblood GE, Gordon RS. *Ceramics International* 1978;4:93–8.
- [2] Takenaka T, Sakata K. *Japanese Journal of Applied Physics* 1980;19:31-9.
- [3] Hirao K, Ohashi M, Brito ME, Kanzaki, S. *Journal of the American Ceramic Society* 1995;78:1687–90.
- [4] Sun SW, Pan XM, Wang PC, Zhu LH, Huang QW, Li DL, Yin ZW. *Applied Physics Letters* 2004;84:574–7.
- [5] Messing GL, Trolier-McKinstry S, Sabolsky EM, Duran C, Kwon S, Brahmaraouty B, Park P, Yilmaz H, Rehrig PW, Eitel KB, Suvaci E, Seabaugh M, Oh KS. *Critical Reviews in Solid State and Materials Sciences* 2004;29:45–96.
- [6] Yilmaz H, Messing GL, Trolier-Mc-Kinstry S. *Journal of Electroceramics* 2003, 11:207-215 and 2003, 11:217-26
- [7] Williamson O. particles orientation in clays and whitewares and relation to forming processes in Ceramic fabrication processes, W.D. Kingering Editor. The Technology Press, MIT, Cambridge, MA,1958.
- [8] Pentecost JL. Wright CH. Preferred orientation in ceramic materials due to forming techniques, in *Advances in X-ray analysis*, G.R. Mallet, M. Fay, W. M. Mueller editors. Plenum Press, NewYork, 1964
- [9] Gao F, Hong RZ, Liu JJ, Yao YH, Tian CS. *Journal of Electroceramics* 2010, 24:145-152
- [10] Sugawara T, Nomura T, Kimura T, Tani T. *Journal of the Ceramic Society of Japan* 2001;109:897-900.
- [11] Sato T, Yoshida Y, Kimura T. *Journal of the American Ceramic Society* 2007;90:3005-8

- [12] Kimura T, Miura Y, Fuse K. International Journal of Applied Ceramic Technology 2005;2:15-23.
- [13] Sato T, Kimura T. Ceramics International 2008;4:757-60.
- [14] Chang YF, Yang ZP, Trolier-McKinstry S, Messing GL. Applied Physics Letters 2009;95:222905.
- [15] Hussain A, Kim JS, Song TK, Kim MH, Kim WJ, Kim SS. Current Applied Physics, 2013, 13:1055-59
- [16] Hao JG, Ye CG, Shen B, Zhai JW. Physica Status Solidi A; 2012, 209:1342-1349
- [17] Chang Y, Chao YZ, Liu Z, Wang Z. Materials Chemistry and Physics 2008;111:195-200
- [18] Geffroy PM, Chartier T, Silvain JF. Journal of the European Ceramic Society 2007;27:291–9.
- [19] Ikeda M, Yoshida M, Satoh A, Nishiyama K, Izumi F, Asano H. Japanese Journal of Applied Physics 1991;30:2295-98.
- [20] Lotgering FK. Journal of Inorganic & Nuclear Chemistry 1959;9:113

	T_C (K)	T_0 (K)	C (K)
BaTiO ₃ – 8% volume NaNbO ₃ textured sample T > 408 K	/	94 ± 5	233167 ± 3400
BaTiO ₃ – 8% volume NaNbO ₃ textured sample T < 408 K	/	243 ± 5	122440 ± 5900
Undoped BaTiO ₃	400 ± 5	370 ± 5	138500 ± 5600

Table 1: Calculated values for the Curie-Weiss plot of fig. 3.b (1 MHz)

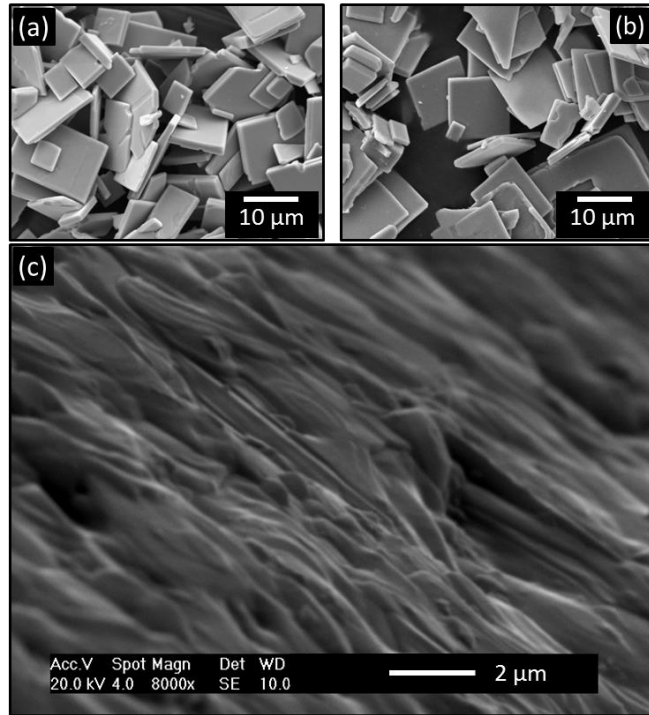


Fig. 1: SEM picture of (a) Bi_{2.5}Na_{3.5}Nb₅O₁₈ platelets obtained by Molten Salts Synthesis, (b) NaNbO₃ templates obtained by Topochemical Conversion (c) BaTiO₃ – 8% volume NaNbO₃ textured sample (fracture).

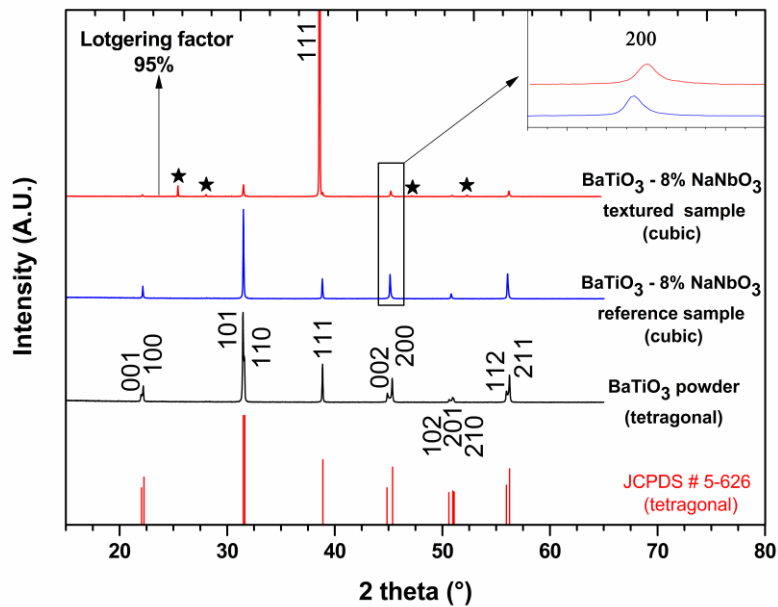


Fig. 2: X-ray diffraction patterns ($\theta/2\theta$, Cu $K\alpha_1$, color online): BaTiO₃ – 8% volume NaNbO₃ textured sample (stars = unidentified secondary phase), BaTiO₃ – 8% volume NaNbO₃ reference sample, tetragonal "pure" BaTiO₃ powder. Insert = detail showing the lack of splitting for (200) peak (the scale is different).

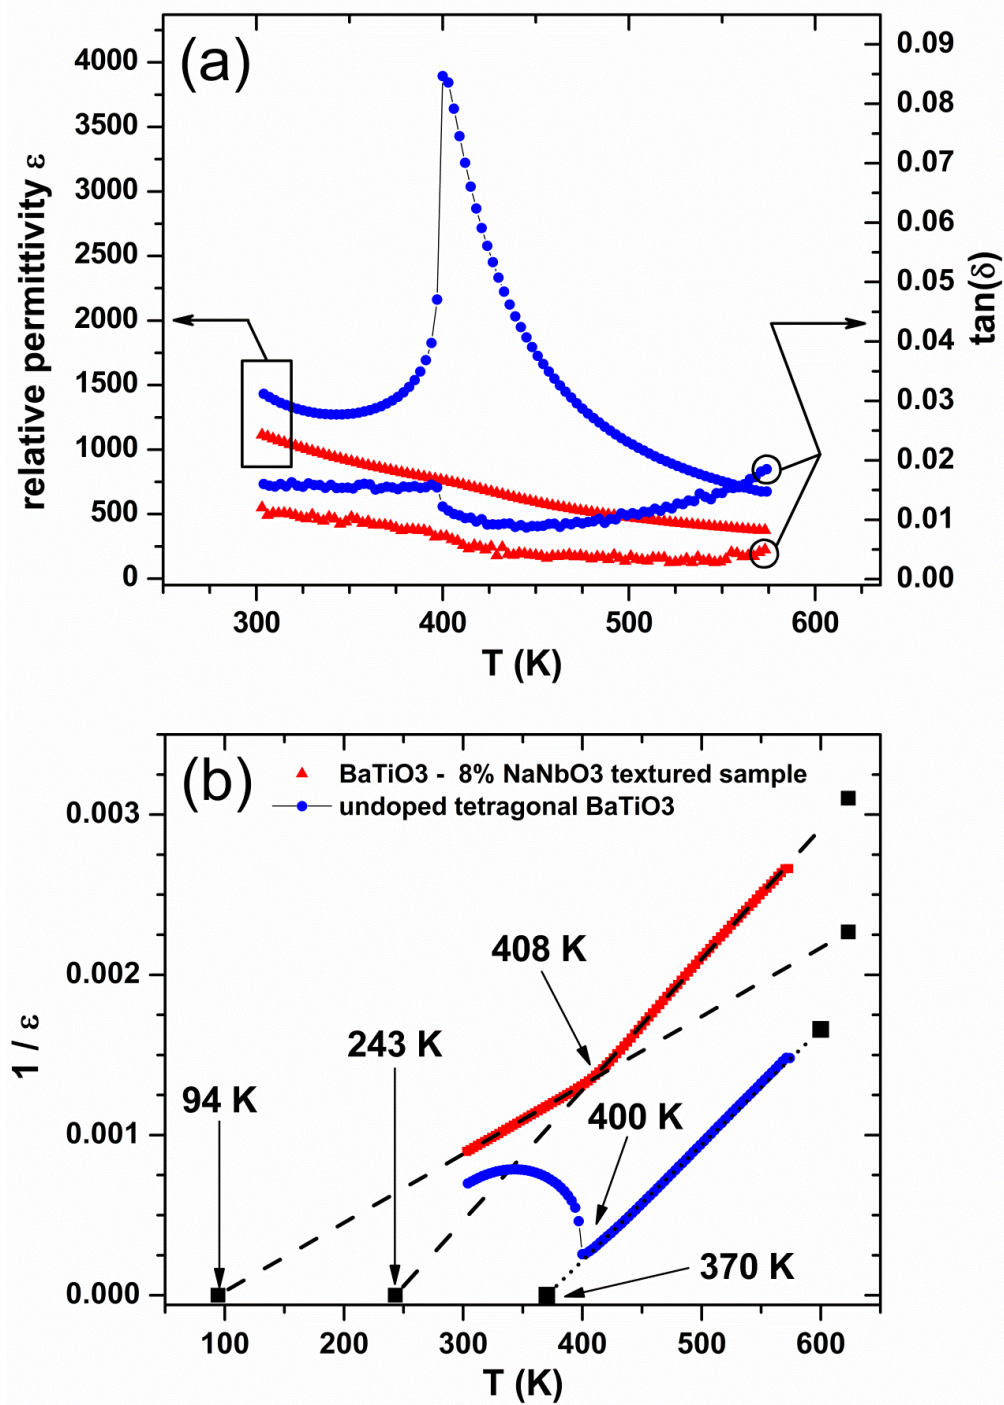


Fig. 3: BaTiO₃ – 8% volume NaNbO₃ textured sample and tetragonal "pure" BaTiO₃ ceramic (color online): (a) relative permittivity and dielectric losses versus temperature (1 MHz), (b) reciprocal relative permittivity versus temperature (Curie-Weiss law, 1 MHz).